

Code 122E: Gravillon 10/16 ETAVAUX Lavé

Producteur : GKM - Carrières d' Etavaux
Petrographie : Gréso-Schisteux
Elaboration : Concassé Lavé

Partie contractuelle


Valeurs spécifiées sur lesquelles le producteur s'engage

Classe granulaire	Norme												CODE
	Norme NF P 18-545 Article 10												
	d/2	d	D	1.4D									
	5	10	16	22.4	31.5	f	FI	AS	C	LA	MBF	S	WA24
Incertitude U	1	5	5	1	0	0.3	4	0.15	0.003	3	2	0.1	0.5
V.S.S.+U	6.0	22.0	100.0	100.0	100.0	1.80	24.00	0.350	0.013	28	12.00	0.500	3.0
V.S.S.	5.0	17.0	99.0	100.0	100.0	1.50	20.00	0.200	0.010	25	10.00	0.400	2.5
V.S.I.	0.0	3.0	84.0	98.0	100.0	0.00							
V.S.I.-U	0.0	0.0	79.0	97.0	100.0	0.00							
Ecart-type max	1.52	4.55	4.55										

Partie informative

Résultats de production

	du 21/07/20 au 07/12/20							du 31/07/20 au 31/07/20					
	5	10	16	22.4	31.5	f	FI	AS	C	LA	MBF	S	WA24
Maximum	1.0	14.1	99.0	100.0	100.0	0.30	14.65						
Xf+1.25xEcart-types	0.9	12.3	98.2	100.0	100.0	0.29							
Moyenne Xf	0.6	8.0	94.9	100.0	100.0	0.19	11.97	0.028	0.001	16	3.66	0.019	0.5
Xf-1.25xEcart-types	0.2	3.8	91.5	100.0	100.0	0.09							
Minimum	0.1	4.3	88.7	100.0	100.0	0.04	9.26						
Ecart-type	0.29	3.44	2.70	0.00	0.00	0.082	1.756						
Nombre de résultats	16	16	16	16	16	16	6	1	1	1	1	1	1

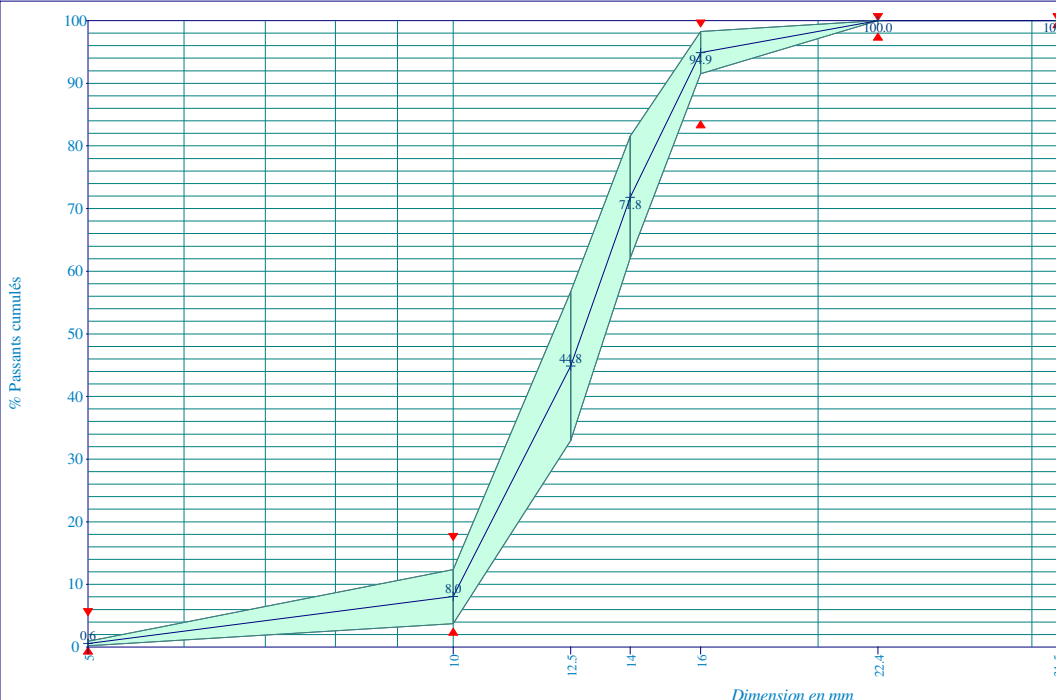

Moyenne	
Fuseau de fabrication	
NFP18545/10:A	
Autres caractéristiques	
Alcali-réaction	NR (31/07/2020)
Sensibilité au gel/dégel	Non gélif (31/07/2020)
Impureté prohibé	Néant (31/07/2020) <0.1
Teneur en alcalins actifs	0.0056 (31/07/2020)
Masse volumique réelle	2.65 (31/07/2020)

Jérémy LEBARBHEY - Nicolas GOSSELIN